

MICROCOPY RESOLUTION TEST CHART NATIONAL BUREAU OF STANDARDS 1965 A

REPORT DOCUMENTATION PAGE		READ INSTRUCTIONS BEFORE COMPLETING FORM	
REPORT NUMBER Technical Report No. 16	2. GOVT ACCESSION NO.	3. RECIPIENT'S CATALOG NUMBER	
TITLE (and Subtitio)		5. TYPE OF REPORT & PERIOD COVERED	
The Application of Infrared Microscopy to the Study of Polymer Fatigue		Technical Report	
		6. PERFORMING ORG. REPORT NUMBER	
AUTHOR(e)		8. CONTRACT OR GRANT NUMBER(*)	
M. T. Hahn, R. W. Hertzberg, Manson, J. C. Michel, A. Ramand S. M. Webler	N00014-77-C-0633		
PERFORMING ORGANIZATION NAME AND AD	DRESS	10. PROGRAM ELEMENT, PROJECT, YASK AREA & WORK UNIT NUMBERS	
Materials Research Center Lehigh University		NR356-670	
Bethlehem, PA 18015			
CONTROLLING OFFICE NAME AND ADDRESS		12. REPORT DATE	
Office of Naval Research		December 1982	
800 North Quincy Street Arlington, VA 22217		13. NUMBER OF PAGES	
MONITORING AGENCY HAME & ADDRESS(IF	different from Controlling Office)	15. SECURITY CLASS. (of this report)	
		Unclassified	
		154. DECLASSIFICATION/DOWNGRADING	

16. DISTRIBUTION STATEMENT (of this Report)

This document has been approved for public release; its distribution is unlimited.

17. DISTRIBUTION STATEMENT (of the abstract entered in Block 20, if different from Report)



18. SUPPLEMENTARY NOTES

Prepared for "Deformation, Yield and Fracture of Polymers", Plastics & Rubber Institute (London).

19. KEY WORDS (Continue on reverse side if necessary and identify by block number)

Infrared microscopy

Fatigue

Polymers

Fatigue mechanisms

Polymer blends

Fracture

29. ABSTRACT (Continue on reverse side if necessary and identify by block number)

A model describing the frequency sensitivity of fatigue crack propagation (FCP) of polymers in terms of localized versus generalized specimen heating is examined. The magnitude of heating at the crack tip and across the unbroker ligament of the specimen is measured with an infrared microscope. The results confirm the earlier hypothesis regarding the observed frequency dependence of FCP behavior.

DD 1 JAN 73 1473

OFFICE OF NAVAL RESEARCH

Contract N00014-77-C-1234

Task No. NR 056-670

TECHNICAL REPORT NO. 16

The Application of Infrared Microscopy in the Study of

Polymer Fatigue

bу

M. T. Hahn, R. W. Hertzberg, R. W. Lang, J. A. Manson, J. C. Michel, A. Ramirez, C. M. Rimnac, and S. M. Webler

Submitted for "Deformation, Yield, and Fracture"


Plastics & Rubber Institute

Materials Research Center Coxe Laboratory #32 Lehigh University Bethlehem, PA 18015

December 1982

Reproduction in whole or in part is permitted for any purpose of the United States Government

This document has been approved for public release and sale; its distribution is unlimited.



THE APPLICATION OF INFRARED MICROSCOPY TO THE STUDY OF POLYMER FATIGUE

M. T. Hahn, R. W. Hertzberg, R. W. Lang, J. A. Manson, J. C. Michel, A. Ramirez, C. M. Rimnac and S. M. Webler*

A model describing the frequency sensitivity of fatigue crack propagation (FCP) of polymers in terms of localized versus generalized specimen heating is examined. The magnitude of heating at the crack tip and across the unbroken ligament of the specimen is measured with an infrared microscope. The results confirm the earlier hypothesis regarding the observed frequency dependence of FCP behavior.

INTRODUCTION

The viscoelastic nature of polymeric materials leads to hysteretic heating during cyclic loading. For cyclic loading at constant stress range, $\Delta \sigma$, the rate of heat production per unit volume, $\boldsymbol{\xi}$, is given by (1):

$$\hat{\epsilon} = \pi f D'' \frac{(\Delta \sigma)^2}{4} \tag{1}$$

where f is the cyclic frequency and D" the loss compliance of the material. In unnotched specimens a relatively large portion of the material experiences a high stress so bulk heating may occur (Eq. 1). This may result in a lowering of the modulus or, in extreme cases, actual melting. It should be noted that a decrease in specimen stiffness will lead to greater cyclic damage under load-controlled conditions and will lower the fatigue life. Since the rate of heating increases with increasing test frequency, it follows that fatigue life would decrease in corresponding fashion. We shall define this condition as one reflecting a negative frequency sensitivity.

In fatigue crack propagation (FCP) tests, heating is often localized near the crack tip where the stresses are highest. Barenblatt et al (2) derived an expression for such local temperature elevations for the case where D" does not vary with temperature and the heated area is small compared to the size of the unbroken ligament of the specimen. In this case, the temperature rise, ΔT , is given by:

$$\Delta T (r,\theta) = [D'' f (\Delta K)^2 \Psi (\theta)]/2 ar$$
 (2)

where r and θ are polar coordinates measured from the crack tip, \underline{a} is a coefficient of heat exchange, and Ψ (θ) is a polynomial function of θ and Poisson's ratio. We have suggested that this localized heating can retard FCP

^{*}Materials Research Center, Lehigh University, Bethlehem, PA 18015

rates due to crack-tip blunting which lowers the effective stress intensity range, $\Delta K_{\rm eff}$ (3). As frequency increases, beneficial local heating would be expected to increase and result in further attenuation of the crack velocity. Such frequency sensitivity is defined as being positive, in that FCP rates are lowered with increasing test frequencies. For many polymers, positive frequency sensitivity is maximized when the test temperature is close to the temperature of the beta transition where energy dissipation and crack-tip heating are maximized (3). This phenomenon has also been observed in the vicinity of the alpha transition (4). In similar fashion, Clutton and Williams (5) have argued that thermal blunting due to localized crack-tip heating in impact tests can enhance the effective fracture toughness of polymers.

If the loss compliance of even a precracked polymer sample is very high, however, the unbroken ligament of the sample can heat significantly in an FCP test. As with unnotched samples, this may decrease specimen stiffness, and result in greater damage per cycle. Since this detrimental heating increases with increasing frequency, FCP rates will also increase with increasing test frequency. Such negative frequency sensitivity with respect to FCP response has been observed in impact-modified nylon 66 (6). While it is clear that knowledge of specimen temperatures is important in the study of fatigue, previous studies of FCP have lacked such detailed temperature information. Attermo and Ostberg (7) used a scanning infrared camera to observe temperatures near the crack tips in fatigue of polymers but did not report on the associated FCP rates.

The objective of this paper is to correlate specimen temperature with fatigue crack propagation rates. To this end, temperatures were recorded at the crack tip and across the unbroken ligament of the specimen using an infrared microscope. This instrument has many advantages over other methods including good spatial resolution, fast response time, precise measurement, easy data acquisition, and non-interference with specimen heating. The effects of several material and test variables on specimen temperature rise are described, as well as the effects of such temperature increases on FCP.

EXPERIMENTAL

<u>Materials</u>

The materials examined included: impact-modified nylon 66 (Zytel ST801), poly(vinyl chloride) modified with 6% methyl methacrylate-butadiene-styrene copolymer (PVC-6% MBS), and acrylonitrile-butadiene-styrene graft copolymer (ABS). Impact-modified dry nylon samples (N_n =17,000)(8) were prepared from 8.3 mm thick injection molded plaques. The PVC-6% MBS samples were prepared from material supplied with a weight-average molecular weight, N_w , of 1.69 x 105. ABS specimens were prepared from 4.8 mm thick extruded sheet.

Loss moduli for the above materials were determined by dynamic mechanical spectroscopy using an automated Rheovibron, model DDV-IIIC. The test procedure is reported elsewhere (9).

FCP Testing

ABS, PVC-6% MBS, and impact-modified nylon were machined into compact-type (CT) specimens with a height-to-width ratio, H/W, of 0.6. For the impact-modified nylons and the PVC-6% MBS, W=61.0 mm; the ABS had W=63.5 mm. FCP tests were run at constant load range with R=0.1 on a closed-loop servohydraulic testing machine. A sinusoidal waveform was used and test frequencies ranged from 1 to 100 Hz. Crack lengths were measured using a traveling micro-

scope. It was necessary to interrupt the test to make such measurements, since these interruptions allowed the specimen to cool, hold time periods were kept as brief as possible. The measured crack growth rates, da/dN, were plotted as a function of the stress intensity factor range, ΔK .

Temperature Measurements

Temperature measurements were made using an RM-2B infrared radiometric microscope manufactured by Barnes Engineering Co. and equipped with a 15% lens with a spot size of 75 _m. The lens collects infrared radiation with wavelengths between 2 and 20 _m and sends this radiation to a germanium detector. The resulting signal is amplified and the analog voltage is displayed on a dial which allows direct reading of temperatures from 15 up to 165°C. The microscope was mounted on a Gaertner XYZ positioner which allows traversing in three perpendicular directions. A linear variable differential transducer (LVDT), mounted adjacent to the positioner, measured the movement of the microscope in the direction of crack growth. The output voltages of the LVDT and the IR microscope were connected to an X-Y recorder; temperature-distance profiles were then generated semi-automatically by traversing the microscope in the direction parallel to the crack plane. Temperature profiles and maximum temperatures were periodically monitored throughout a test. All temperature measurements were made while the specimens were being cycled, and therefore represent steady-state measurement for each LK, test frequency, and material condition.

RESULTS AND DISCUSSION

The earlier hypotheses (3,4,6,10) about the interrelation of viscoelastic damping peaks, hysteretic heating, and crack growth rates were confirmed by correlation of FCP data with the infrared temperature measurements and the dynamic mechanical data. These data are shown in Figure 1a-i for three cases: (1) ABS, which shows negligible frequency sensitivity, (2) PVC-6% MBS, which shows positive frequency sensitivity, and (3) impact-modified nylon 66, which shows negative frequency sensitivity.

In the FCP data for ABS, Figure la (10), no significant variation in the growth rates is seen when the frequency varies between 1 and 100 Hz. This is consistent with the measurements of specimen temperature, Figure 1d, which show that negligible heating takes place at the frequencies from 1 to 100 Hz and values of ΔK of up to 1.0 MPa \sqrt{m} . Positive frequency sensitivity is illustrated in Figure 1b for PVC-6% MBS. A decrease in the crack growth rate occurs as the test frequency increases from 10 to 100 Hz. The specimen temperatures, Figure le, show negligible heating at 10 Hz and a AK of 1.4 MPa, m; for the same ΔK value a temperature rise of 9°C is observed at 100 Hz. Note that this temperature rise is localized near the crack tip. We believe that the localized heating at 100 Hz leads to greater crack blunting, thereby ascounting for the lower FCP rates. The FCP data for impact-modified nylon 66 are shown in Figure 1c (6). Note the increase in FCP rates with increasing frequency. (The 30 Hz data correspond to a material containing some unknown amount of water but are believed to correctly represent overall data trends.) This negative frequency sensitivity also may be related to the infrared temperature rise in dry samples is significant at 10 Hz and even greater at 30 Hz. The temperature rises observed are certainly sufficient to lower the value of the modulus, resulting in greater cyclic damage as discussed elsewhere (6).

At this point, it is important to consider why more heating takes place in the impact-modified nylon 66 samples as compared with the PVC-6% MBS and ABS samples. Equation 2 shows that ΔT varies directly with the magnitudes of

• • •

D", test frequency, and $(\Delta K)^2$. In addition, one must be mindful of the rate of change of D" with temperature, dD"/dT; when this parameter is positive and large, specimen heating occurs under autoaccelerating conditions. From Figure lg,h,i we see that D" for the modified nylon 66 is the smallest among the three materials and, yet, this material experiences the greatest amount of heating. This condition is surely traced, in part, to the higher ΔK level (2.9 MPa \sqrt{m}) associated with the temperature measurements of this material as compared with the ABS ($\Delta K-1.0 \text{ MPa}\sqrt{\text{m}}$) and PVC-6% MBS (1.4 MPa $\sqrt{\text{m}}$) polymers. (The ΔK levels chosen for each polymer reflect the relative ranking of the fatigue resistance of these materials.) Also, the D"-gradient, dD"/dT is much greater in the nylon sample over the temperature ranges experienced by these materials. Even greater temperature elevations would be expected in the nylon sample had it been possible to conduct the fatigue test at 100 Hz (the frequency used in the ABS and PVC-6% MBS materials.) Finally, the greater amount of heating found in the PVC-6% MBS material as compared with ABS is traced to the combined influence of higher ΔK values used in the fatigue test and the magnitude of D" in the PVC-6% MBS polymer. Thus it is shown that for the cases of positive, negative, or zero frequency sensitivity, the FCP data correlate well with infrared temperature measurements and the viscoelastic damping data.

The preceding results show specimen temperature distributions at one value of ΔK for each material. Additional studies have shown that crack-tip temperatures increase markedly with increasing levels of ΔK and that the rate of increase in temperature with respect to crack length, dT/da, is linked strongly with the K-gradient, dK/da. We have also found that the second-power dependence of ΔK (Eq.2) holds only when D" for the material in question does not vary over the temperature range encountered. Finally, it has been shown that the degree of heating depends on the specimen configuration. For a given ΔK -level, specimen heating is greater for cases in which the Y-calibration factor of ΔK is low. In this circumstance, the overall cyclic stress level is higher, which contributes to greater hysteretic heating.

CONCLUSIONS

The infrared temperature measurements, together with viscoelastic data, serve to explain positive, negative, and negligible frequency sensitivity in a number of polymers. The observed frequency sensitivity is consistent with previous arguments of the competition between localized and generalized heating. The degree of hysteretic heating was found to depend on the prevailing values of ΔK , test frequency, and loss moduli.

ACKNOWLEDGEMENTS

We thank the Polymers Program of the National Science Foundation (Grant No. DMR 77-10063) and the Chemistry Division of the Office of Naval Research for partial support of this effort. Fellowships for two of the authors were provided by the International Business Machines Foundation (CNR and MTH). E. I. duPont de Nemours and Co., Westlake Plastics, and B. F. Goodrich provided materials for this study.

REFERENCES

- 1. Ferry, J. D., "Viscoelastic Properties of Polymers," John Wiley, New York, 575 (1961).
- 2. Barenblatt, G. I., Entov, V. M. and Salganik, R. L., <u>IUTAM Symp</u>. <u>Thermoinelast</u>., East Kilbridge (1968) 33.
- 3. Hertzberg, R. W., Manson, J. A. and Skibo, M. D., <u>Polymer</u>, <u>19</u>, (1978) 358.
- 4. Hertzberg, R. W., Manson, J. A., Lang, R. W. and Bretz, P. E., submitted to Polymer 1981.
- 5. Clutton, E. Q. and Williams, J. G., J. Mater. Sci., 16, (1981) 2583.
- 6. Skibo, M. D., Hertzberg, R. W. and Manson, J. A., Paper 4, <u>Proceedings International Conference on Deformation</u>, Yield and Fracture of Polymers, London (1978).
- 7. Attermo, R. and Ostberg, G., <u>Int. J. Fract. Mech.</u>, <u>7</u>, (1971) 122.
- 8. Zytel Design Handbook, E. I. duPont de Nemours and Co., Wilmington, Delaware (1980).
- 9. Webler, S. M., Manson, J. A. and Lang, R. W., Polymer Preprints, 22(1), (1981) 257.
- Skibo, M. D., Janiszewski, J., Kim, S. L., Hertzberg, R. W. and Manson, J. A., Proc. App. Tech. Meeting 36th SPE, Washington, D.C., (1978) 304.

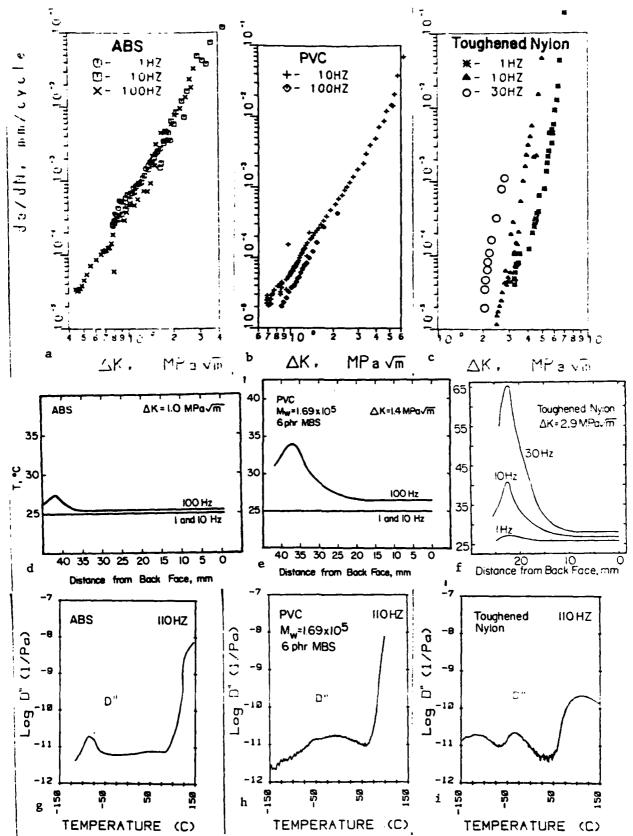


Fig. la,b,c--Fatigue crack growth data for ABS, rubber-modified PVC and toughened nylon, respectively; d,e,f--temperature profiles for the above; g,h,i--loss compliance vs. temperature for the above.

TECHNICAL REPORT DISTRIBUTION LIST, GEN

	No.		No.
	Copies		Copies
Office of Naval Research		Naval Ocean Systems Center	
Attn: Code 413		Attn: Mr. Joe McCartney	
800 North Quincy Street		San Diego, California 92152	1
Arlington, Virginia 22217	2	_	
		Naval Weapons Center	
ONR Pasadena Detachment		Attn: Dr. A. B. Amster,	
Attn: Dr. R. J. Marcus		Chemistry Division	
1030 East Green Street		China Lake, California 93555	. 1
Pasadena, California 91106	1		
		Naval Civil Engineering Laboratory	
Commander, Naval Air Systems Command		Attn: Dr. R. W. Drisko	
Attn: Code 310C (H. Rosenwasser)		Port Hueneme, California 93401	1
Department of the Navy			
Washington, D.C. 20360	1	Dean William Tolles	
		Naval Postgraduate School	
Defense Technical Information Center	•	Monterey, California 93940	1
Building 5, Cameron Station			
Alexandria, Virginia 22314	12	Scientific Advisor	
		Commandant of the Marine Corps	
Dr. Fred Saalfeld		(Code RD-1)	
Chemistry Division, Code 6100		Washington, D.C. 20380	1
Naval Research Laboratory	_		
Washington, D.C. 20375	1	Naval Ship Research and Development	
		Center	
U.S. Army Research Office		Attn: Dr. G. Bosmajian, Applied	
Attn: CRD-AA-IP		Chemistry Division	_
P. O. Box 12211		Annapolis, Maryland 21401	1
Research Triangle Park, N.C. 27709	1		
		Mr. John Boyle	
Mr. Vincent Schaper		Materials Branch	
DTNSRDC Code 2803	•	Naval Ship Engineering Center	
Annapolis, Maryland 21402	1	Philadelphia, Pennsylvania 19112	1
Naval Ocean Systems Center		Mr. A. M. Anzalone	
Attn: Dr. S. Yamamoto		Administrative Librarian	
Marine Sciences Division		PLASTEC/ARRADCOM	
San Diego, California 91232	1	Bldg 3401	
		Dover, New Jersey 07801	1

TECHNICAL REPORT DISTRIBUTION LIST, 356A

	No. Copies		No. Copies
Dr. M. Broadhurst		Dr. K. D. Pae	
Bulk Properties Section		Department of Mechanics and	
National Bureau of Standards		Materials Science	
U. S. Department of Commerce	_	Rutgers University	
Washington, D.C. 20234	2	New Brunswick, New Jersey 08903	1
Naval Surface Weapons Center		NASA-Lewis Research Center	
Attn: Dr. J. M. Augl,		Attn: Dr. T. T. Serofini, MS-49-1	
Dr. B. Hartman		2100 Brookpark Road	
White Oak		Cleveland, Ohio 44135	1
Silver Spring, Maryland 20910	1		
		Dr. Charles H. Sherman	
Dr. G. Goodman		Code TD 121	
Globe Union Incorporated		Naval Underwater Systems Center	
5757 North Green Bay Avenue	_	New London, Connecticut 06320	1
Milwaukee, Wisconsin 53201	1		
		Dr. William Risen	
Professor Hatsuo Ishida		Department of Chemistry	
Department of Macromolecular Science	!	Brown University	_
Case-Western Reserve University	•	Providence, Rhode Island 02191	1
Cleveland, Ohio 44106	1	M. B. L	
Dr. Dond I Come		Mr. Robert W. Jones	
Dr. David Soong		Advanced Projects Manager	
Department of Chemical Engineering		Hughes Aircraft Company	
University of California Berkeley, California 94720		Mail Station D 132	•
Berkeley, California 74720		Culver City, California 90230	1
Dr. Curtis W. Frank		Dr. C. Giori	
Department of Chemical Engineering		IIT Research Institute	
Stanford University		10 West 35 Street	
Stanford, California 94035		Chicago, Illinois 60616	
Picatinny Arsenal		Dr. R. S. Roe	
Attn: A. M. Anzalone, Building 3401		Department of Materials Science	
SMUPA-FR-M-D		and Metallurgical Engineering	
Dover, New Jersey 07801	1	University of Cincinnatti	
•		Cincinnati, Ohic 45221	· 1
Dr. J. K. Gillham		•	_
Department of Chemistry		Dr. Robert E. Cohen	
Princeton University		Chemical Engineering Department	
Princeton, New Jersey 08540	1	Massachusetts Institute of Technolog	y
		Cambridge, Massachusetts 02139	1
Dr. E. Baer			
Department of Macromolecular		Dr. T. P. Conlon, Jr., Code 3622	
Science		Sandia Laboratories	
Case Western Reserve University		Sandia Corporation	
Cleveland, Ohio 44106	1	Albuquerque, New Mexico	1
·			

TECHNICAL REPORT DISTRIBUTION LIST, 356A

	No.		No.
	Copies		Copies
Dr. Martin Kaufman			
Code 38506		Professor C. S. Paik Sung	
Naval Weapons Center		Department of Materials Sciences and	
China Lake, California 93555	1	Engineering Room 8-109	
		Massachusetts Institute of Technology	7
Professor S. Senturia		Cambridge, Massachusetts 02139	1
Department of Electrical Engineering		·	
Massachusetts Institute of Technology	•	Professor Brian Newman	
Cambridge, Massachusetts 02139	1	Department of Mechanics and	
		Materials Science	
Dr. T. J. Reinhart, Jr., Chief		Rutgers, The State University	
Composite and Fibrous Materials Branc	:h	Piscataway, New Jersey 08854	1
Nonmetallic Materials Division			
Department of the Air Force		Dr. John Lundberg	
Air Force Materials Laboratory (AFSC)		School of Textile Engineering	
Wright-Patterson AFB, Ohio 45433	1	Georgia Institute of Technology	
		Atlanta, Georgia 30332	1
Dr. J. Lando			
Department of Macromolecular Science			
Case Western Reserve University			
Cleveland, Ohio 44106	1		
Dr. J. White			
Chemical and Metallurgical Engineerin	•		
University of Tennessee	· 5		
Knoxville, Tennessee 37916	1	•	
	-		
Dr. J. A. Manson-			
Materials Research Center		•	
Lehigh University			
Bechlehem, Pennsylvania 18015	1		
Dr. R. F. Helmreich			
Contract RD&E			
Dow Chemical Co.			
Midland, Michigan 48640	1		
midiand, michigan 40040	1		
Dr. R. S. Porter			
Department of Polymer Science			
and Engineering			
University of Massachusetts			
Amherst, Massachusetts 01002	1	•	
Professor Garth Wilkes			
Department of Chemical Engineering			
Virginia Polytechnic Institute and			
State University			
Blacksburg, Virginia 24061	1		
Presidents, trebunte tinns	•		

END DATE FILMED

2-83

DTIC